

Bostik SA  
420 rue d'Estienne d'Orves  
92700 Colombes  
FRANCE

**Eurofins Product Testing A/S**  
Smedeskovvej 38  
8464 Galten  
Denmark

CustomerSupport@eurofins.com  
www.eurofins.com/voc-testing

Date  
22 April 2020

# EMICODE Test Report

## 1 Sample Information

Sample identification	SL C340 LEVEL PLUS
Batch no.	15/06/2015 00003360 17:46
Production date	15/06/2015
Product type	Levelling compound
Date when sample was received	01/07/2015
Testing (start - end)	07/07/2015 - 04/08/2015

## 2 Evaluation of the Results

The tested product complies with the requirements of GEV and the results correspond to the EMICODE emission class EC 1 PLUS.

Parameter	Concentration $\mu\text{g}/\text{m}^3$	EC 2 $\mu\text{g}/\text{m}^3$	EC 1 $\mu\text{g}/\text{m}^3$	EC 1 Plus $\mu\text{g}/\text{m}^3$
<b>TVOC 3 days</b>	33	$\leq 3000$	$\leq 1000$	$\leq 750$
<b>TVOC 28 days</b>	< 5	$\leq 300$	$\leq 100$	$\leq 60$
<b>TSVOC 28 days</b>	< 5	$\leq 100$	$\leq 50$	$\leq 40$
<b>Total VOC without NIK 28 days</b>	< 5	>40		$\leq 40$
<b>R-value (dimensionless) 28 days</b>	0	>1		$\leq 1$
<b>Formaldehyde 3 days</b>	< 3	$\leq 50$		
<b>Acetaldehyde 3 days</b>	6.8	$\leq 50$		
<b>Sum Formaldehyde + Acetaldehyde 3 days (ppm)</b>	< 0.005	$\leq 0.05$		
<b>Total Carcinogens 3 days</b>	< 1	$\leq 10$		
<b>Total Carcinogens 28 days</b>	< 1	$\leq 1$		

This test report does not alone entitle to use the protected trademark label EMICODE. For the use of an EMICODE label a license has to be applied for at the GEV, Düsseldorf, Germany. A license can only be granted for ready-to-use products, if some additional requirements on contents of certain chemicals (e.g. solvent-free) are fulfilled.

Note: The label is supplemented with a final letter R (e.g. EMICODE EC 1 R) for installation products that fulfill the specification in clause 3.1.2 sentence 2 of GEV classification criteria and that therefore may require measures for ensuring occupational safety during application.

The results are only valid for the tested sample(s).

This report may only be copied or reprinted in its entity, parts of it only with a written acceptance by Eurofins.

## Table of contents

<b>1</b>	<b>Sample Information</b>	<b>1</b>
<b>2</b>	<b>Evaluation of the Results</b>	<b>1</b>
<b>3</b>	<b>Test Method</b>	<b>2</b>
<b>4</b>	<b>Results</b>	<b>3</b>
4.1	Emission Test after 3 Days	3
4.2	Emission Test after 28 Days	4
4.3	Chromatograms	5
<b>5</b>	<b>Appendices</b>	<b>6</b>
5.1	Description of the applied test method	6

## 3 Test Method

Method	Principle	Parameter	Quantification limit	Uncertainty
GEV method in its version of 15.04.2013.				
Internal method numbers: 9810, 9811, 9812, 2808B, 8400	GC/MS	VVOC, VOC, SVOC	5 µg/m <sup>3</sup>	22% (RSD)
	HPLC	Volatile aldehydes	3 µg/m <sup>3</sup>	Um = 2 x RSD = 45 %
<b>Test chamber parameter</b>				
Chamber volume, l	119	Temperature, °C	23±1	Relative humidity, %
Air change rate, 1/h	0.5	Loading ratio, m <sup>2</sup> /m <sup>3</sup>	0.4	50±3
<b>Sample preparation</b>				
The sample was mixed homogeneously, 400 g material in 96 g water. A part of the mixture was spread on to a glass plate and drawn off over a model giving a 3 mm thick and uniform layer.				
<b>Deviations from the test method</b>	None			

For detailed method description see: Description of the applied test method

## 4 Results

### 4.1 Emission Test after 3 Days

	CAS No.	Retention time min	ID-Cat.	Concentration µg/m <sup>3</sup>	NIK-value µg/m <sup>3</sup>	R-value	Emission rate µg/(m <sup>2</sup> *h)	Toluene equivalent µg/m <sup>3</sup>
<b>TVOC (C6-C16)</b>				51			64	<b>33</b>
<b>VOC with NIK</b>								
Methylene glycol *	109-86-4	2.38	1	< 5	3	-	< 7	< 5
1-Methoxy-2-propanol *	107-98-2	2.72	1	33	3700	0.0089	41	14
Phenol *	108-95-2	8.22	1	< 5	10	-	< 7	< 5
2-Ethyl-1-hexanol	104-76-7	8.95	1	< 5	540	-	< 7	< 5
2-Phenoxy ethanol *	122-99-6	11.38	1	< 5	1100	-	< 7	< 5
Saturated aliphatic hydrocarbons higher than C9 *	-	10.7-11.4	2	18	6000	0.0031	23	18
<b>R-value = <math>\sum \text{Conc}_i/\text{NIK}_i</math></b>						0.012		
<b>VOC without NIK</b>								
Not identified *	-	2.61	4	< 5	-	-	< 7	< 5
Not identified *	-	3.59	4	< 5	-	-	< 7	< 5
Not identified *	-	4.84	4	< 5	-	-	< 7	< 5
Not identified *	-	6.04	4	< 5	-	-	< 7	< 5
Not identified *	-	6.88	4	< 5	-	-	< 7	< 5
Not identified *	-	11.89	4	< 5	-	-	< 7	< 5
Not identified *	-	11.98	4	< 5	-	-	< 7	< 5
<b>Total VOC without NIK</b>				< 5			< 7	< 5
<b>Total VVOC (&lt; C6)</b>				< 5			< 7	< 5
n.d.	-	-	-	< 5	-	-	< 7	< 5
<b>Total SVOC (&gt; C16)</b>				< 5			< 7	< 5
n.d.	-	-	-	< 5	-	-	< 7	< 5
<b>Total Carcinogens</b>				< 1			< 2	< 1
<b>Volatile Aldehydes C1-C2 measured with DNPH-Method ( see 5.1.4)</b>								
Formaldehyde	50-00-0	-	-	< 3		-	< 4	-
Acetaldehyde	75-07-0	-	-	6.8	-	-	8.5	-
<b>Sum Formaldehyde + Acetaldehyde (ppm)</b>	-	-	-	<0.005	ppm	-	-	-

n.d. Not detected

< Means less than

\* Not a part of our accreditation. See 5.3.6 Accreditation

a The method is not optimal for very volatile compounds. For these substances smaller results and a higher uncertainty in the measurement cannot be excluded.

The results are only valid for the tested sample(s).

This report may only be copied or reprinted in its entity, parts of it only with a written acceptance by Eurofins.

## 4.2 Emission Test after 28 Days

	CAS No.	Retention time min	ID-Cat.	Concentration $\mu\text{g}/\text{m}^3$	NIK-value $\mu\text{g}/\text{m}^3$	R-value	Emission rate $\mu\text{g}/(\text{m}^2\cdot\text{h})$	Toluene equivalent $\mu\text{g}/\text{m}^3$
<b>TVOC (C6-C16)</b>				< 5			< 7	< 5
<b>VOC with NIK</b>								
Hexanal	66-25-1	4.67	1	1.2	890	-	1.5	< 1
<b>R-value = <math>\sum \text{Conc}/\text{NIK}_i</math></b>						<b>0</b>		
<b>VOC without NIK</b>								
n.d.	-	-	-	< 5	-	-	< 7	< 5
<b>Total VOC without NIK</b>				< 5			< 7	< 5
<b>Total VVOC (&lt; C6)</b>				< 5			< 7	< 5
n.d.	-	-	-	< 5	-	-	< 7	< 5
<b>Total SVOC (&gt; C16)</b>				< 5			< 7	< 5
n.d.	-	-	-	< 5	-	-	< 7	< 5
<b>Total Carcinogens</b>				< 1			< 2	< 1

n.d. Not detected

< Means less than

\* Not a part of our accreditation. See 5.3.6 Accreditation

a The method is not optimal for very volatile compounds. For these substances smaller results and a higher uncertainty in the measurement cannot be excluded.

### Categories of identity:

- 1: Identified and specifically calibrated
- 2: Identified by comparison with a mass spectrum obtained from a library and supported by other information. Calibrated as toluene equivalent
- 3: Identified by comparison with a mass spectrum obtained from a library. Calibrated as toluene equivalent
- 4: Not identified. Calibrated as toluene equivalent




Maria Pelle  
Chemist




Rasmus Stengaard Christensen  
Analytical Service Manager, MSc in Chemistry

## 4.3 Chromatograms

### 4.3.1 Chromatogram after 3 days

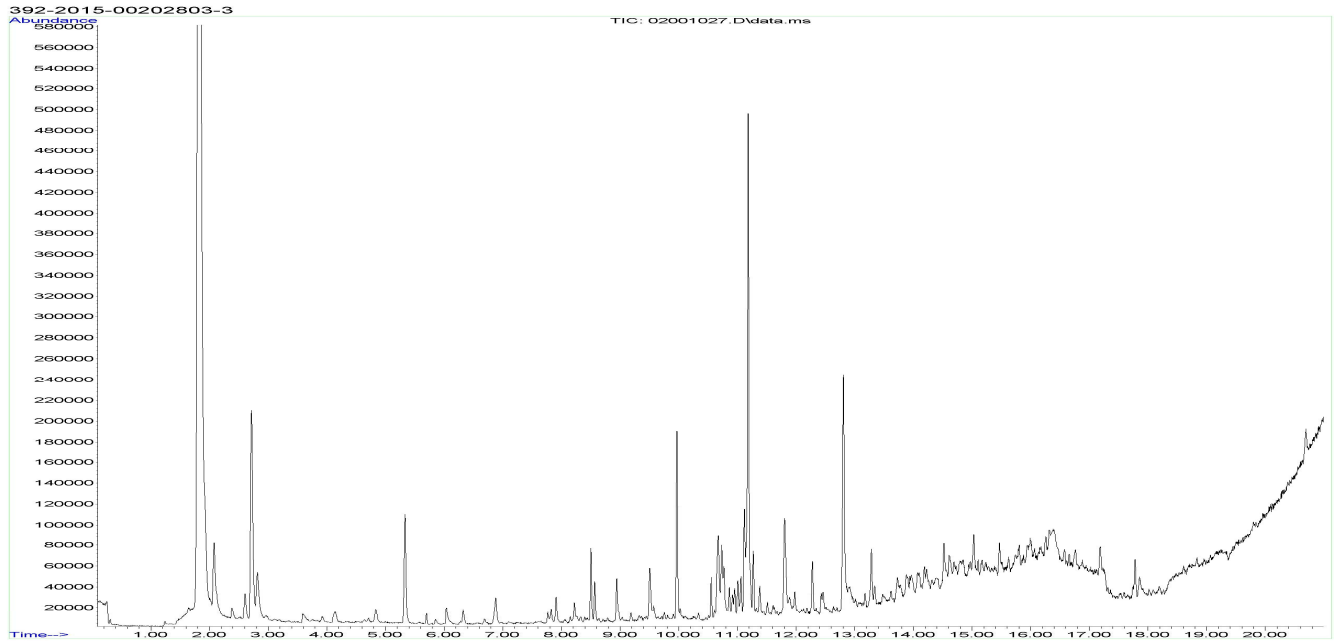

### 4.3.2 Chromatogram after 28 days

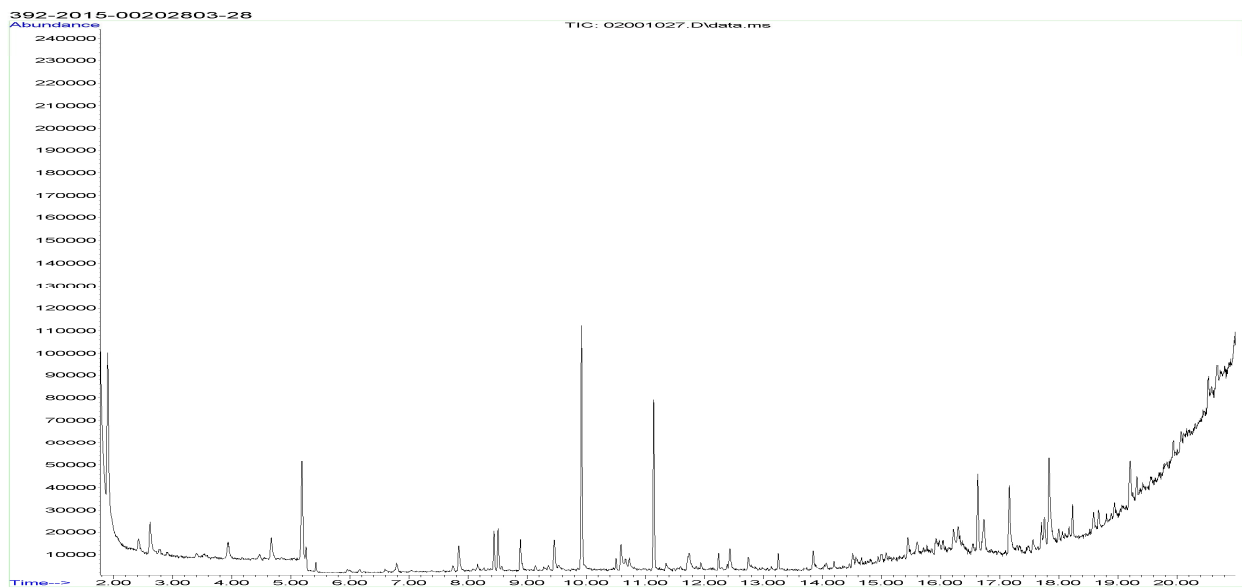

Please consider the different scales

The results are only valid for the tested sample(s).

This report may only be copied or reprinted in its entity, parts of it only with a written acceptance by Eurofins.

## 5 Appendices

### 5.1 Description of the applied test method

#### 5.1.1 Test Chamber

The test chamber is made of stainless steel. A multi-step air clean-up is performed before loading the chamber, and a blank check of the empty chamber is performed. The operation parameters are 23 °C, 50 % relative air humidity in the supply air.

#### 5.1.2 Sampling, Desorption, Analyses

##### Testing for Carcinogens

The presence of carcinogens (EU Categories C1 and C2, as per the latest publication on the homepage of German BGIA Institute) was tested by drawing sample air from the chamber outlet through 2 Tenax TA tubes (main tube and backup tube). Analysis was performed by thermal desorption and gas chromatography / mass spectroscopy (internal methods no.: 9812 / 2808B). The absence of a listed carcinogen was stated if the specific combination of fragment ions was absent at the specific retention time in the chromatogram. If no listed carcinogens were found but the required detection limit was exceeded, the identity was checked by comparing full scan sample mass spectra with full scan standard mass spectra.

This test covered only substances that can be adsorbed on to Tenax TA and that can be thermally desorbed. If other emissions occurred, then these substances cannot be detected (or with limited reliability only).

##### VOC Emission Testing

The emissions of organic compounds were tested by drawing sample air from the chamber outlet through 2 Tenax TA tubes (main tube and backup tube). Analysis was performed by thermal desorption and gas chromatography / mass spectroscopy (internal methods no.: 9812 / 2808B).

All single substances that are listed with a NIK value in the latest AgBB publication were identified. Quantification was done with the respective response factor and the TIC signal or in case of overlapping peaks by calculating with fragment ions. All other single substances, as well as all non-identified substances, were quantified as toluene equivalent.

The results of the individual substances were calculated in three groups depending on their appearance in a gas chromatogram when analysing with a non-polar column:

- Volatile organic compounds VOC: All substances appearing between these limits.
- Semi-volatile organic compounds SVOC: All substances appearing after n-hexadecane (n-C16).
- Very volatile organic compounds VVOC: All substances appearing before n-hexane (n-C6).

Calculation of the TVOC (Total Volatile Organic Compounds) was performed according to the AgBB/DIBt test method, by addition of the results of all individual substances with concentrations = 5 µg/m<sup>3</sup> in the retention time interval C6-C16. Furthermore the TVOC was calculated as the toluene equivalent, as defined in ISO 16000-6.

Calculation of the TSVOC (Total Semi-Volatile Organic Compounds) was performed by addition of the results of all substances with concentrations = 5 µg/m<sup>3</sup> between C16 and C22 as toluene equivalent, as defined in ISO 16000-6.

Calculation of the TVVOC (Total Very Volatile Organic Compounds) was performed by addition of the results of all substances with concentrations = 5 µg/m<sup>3</sup> appearing before C6 as toluene equivalent, as defined in ISO 16000-6.

This test covered only substances that can be adsorbed on Tenax TA and that can be thermally desorbed. If other emissions occurred then these substances cannot be detected (or with limited reliability only).

### 5.1.3 Calculation of R Values with the German NIK List

The concentrations of all substances = 5 µg/m<sup>3</sup> in the interval between n-C6 and n-C16 were divided by their respective NIK value (if given). The sum of the quotients gives the R value:

$$R = \sum_i^n \left( \frac{c_i}{\text{NIK}_i} + \dots + \frac{c_n}{\text{NIK}_n} \right)$$

In addition, all results were summed up for the substances without published NIK value, but in the interval between n-C6 and n-C16, when concentrations were = 5 µg/m<sup>3</sup>.

### 5.1.4 Testing of Aldehydes

The presence of aldehydes was tested by drawing air samples from the chamber outlet through DNPH-coated silicagel tubes. Analysis was done by solvent desorption, HPLC and UV-/diode array detection (ISO 16000-3, internal methods no.: 9812 / 8400).

The absence of formaldehyde was stated if the specific wavelength UV detector response was lacking at the specific retention time in the chromatogram. Otherwise it was checked whether the detection limit was exceeded. In this case the identity was finally checked by comparing full scan sample UV spectra with full scan standard UV spectra.

### 5.1.5 Quality assurance

Before loading the chamber a blank check of the empty chamber was performed and compliance with background concentrations in accordance with ISO 16000-9 was determined. Sampling at the chamber outlet and subsequent analysis was performed in duplicate. For monitoring any breakthrough or overloading of the tubes, two Tenax TA tubes were used in series.

In each sequence stability of GC system was checked by a general function test of device and column, and by use of control charts for monitoring mean values and standard deviations for individual VOCs. Reproducibility of the method was monitored for two selected VOCs per sequence.

### 5.1.6 Accreditation

The testing methods described above are accredited to EN ISO/IEC 17025:2005 by DANAK (no. 522). Not all parameters are covered by this accreditation. At present the accreditation does not cover the parameters marked with a note \*, however analysis was performed for these parameters at the same level of quality as for the accredited parameters.

### 5.1.7 Uncertainty of the test method

The relative standard deviation (RSD) of the test method amounts to 22%. The expanded uncertainty  $U_m$  is 45% and equals 2 x %RSD. For further information please visit [www.eurofins.dk/uncertainty](http://www.eurofins.dk/uncertainty).